



STRATASYS F123 TPU 92A BEST PRACTICES

November 2018

stratasys[®]

IMPORTANT CONSIDERATIONS ABOUT F123 TPU 92A MATERIAL

This document is intended to point out the key differentiations and how to get the best results in printing parts with F123 TPU 92A material (also known as FDM® TPU 92A)

Applicable Documents:


- F123 User Guide
 - Please refer to the Troubleshooting section of the F123 User guide for possible issues related to system operation
 - Available on the Stratasys.com website:
 - <http://articles.stratasys.com/user-guides/fdm-3d-printers/f123-series-user-guide>
- F123 TPU 92A Material Guide
 - Detailed technical guide to optimize print success for specific applications with the TPU material
- F123 Series TPU 92A Quick Start Guide
 - Included in the F123 TPU 92A Upgrade Kit

GENERAL INFORMATION

ELASTOMER EXTRUSION KIT


Contents:

- F123 TPU 92A extrusion head - Qty 1
- F123 TPU 92A filament spool, black - Qty 1
- Brochure with installation instructions - Qty 1
- Modified Upper Y Block - Qty 2

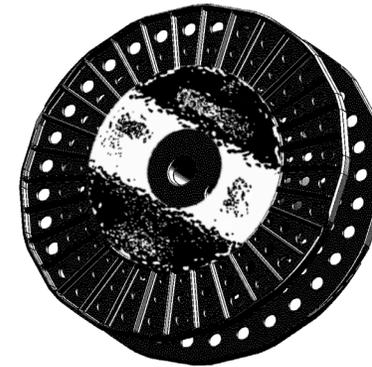

The kit can be installed by customers

TPU FILAMENT SPOOLS

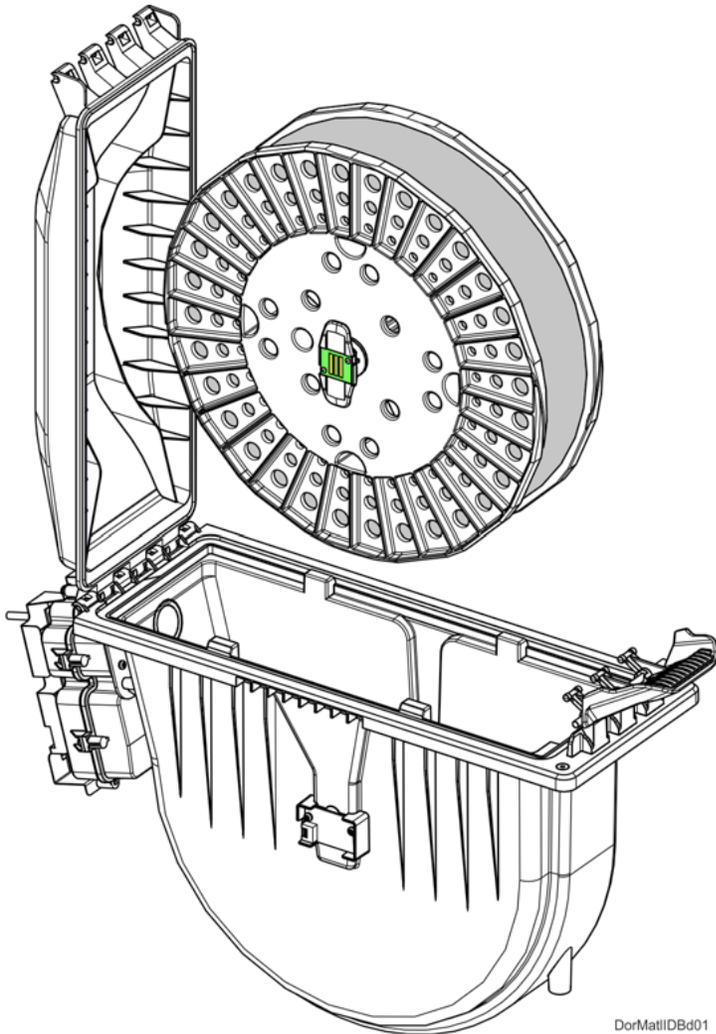

Spools:

Same spool consumable as F123 platform

Filament tail clips to spool OD

- Make sure to remove orange tape before loading

System Behavior:

- Load is slower for both model and support: approx. 60 vs. 10 seconds.
- Auto Change/Unload behavior
 - The printer isn't intended to swallow the tail of the TPU material (meaning the head can't push the material back through the filament detect switch)
 - Because the tail isn't swallowed, material will be left on the spool (approximately 20-150 feet will be left on the spool after it is marked empty. This number may vary based on machine and part geometry and is not counted as part of the 60 ci spool volume.

TPU MATERIAL HANDLING

- **Proper storage of materials is critical.**
- When removing TPU spools from the system, place the material spool in the Mylar bag immediately.
- For extended non-use periods greater than 48 hours, unload the material from the head and wind back onto the spool. Store in the material bay.
- (Environments with high humidity should unload the material after 36 hours)
- Note: If the machine has been idle with TPU material loaded for more than 48 hours, unload the filament and cut off 6 ft. (1.8 m) of the filament end and reload into the printer

PART ACCURACY


- Parts are produced within an accuracy of: +/- .254 mm (.010 in), or +/- .003 mm/mm (.003 in/in), whichever is greater
 - Accuracy is geometry-dependent. Achievable accuracy specification derived from statistical data at 95% dimensional yield.
 - Z part accuracy includes an additional tolerance of -0.000/+slice height.
- Putting printed parts into a support removal tank may cause swelling of up to 0.5%, which can result in the part being out of the accuracy tolerance initially.
 - Depending on part size and geometry it may take up to 72 hours for a part to shrink back to pre-tanked size.
- Due to the nature of the elastomer material, the visual quality of parts, particularly fine feature details, may not be as high as it is for rigid materials such as ABS or ASA on the F123 platform

BUILD TRAY HANDLING


For all materials it's important to avoid contamination during handling of the build trays



Placed thumb on clean, new substrate consistent with normal handling conditions. Firm pressure, some movement.

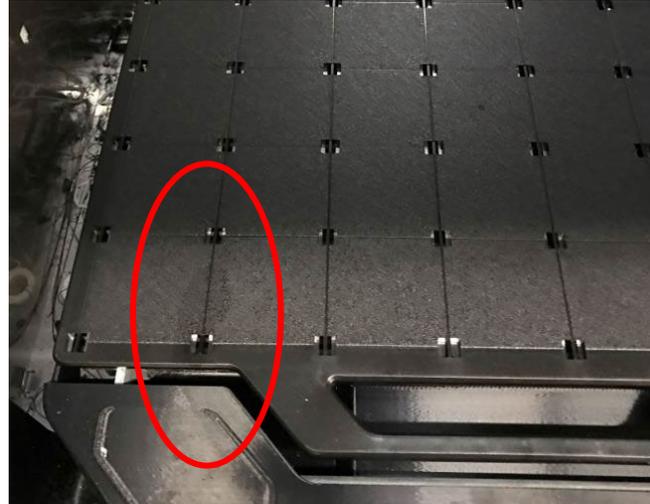


Oil from hand remains on build substrate

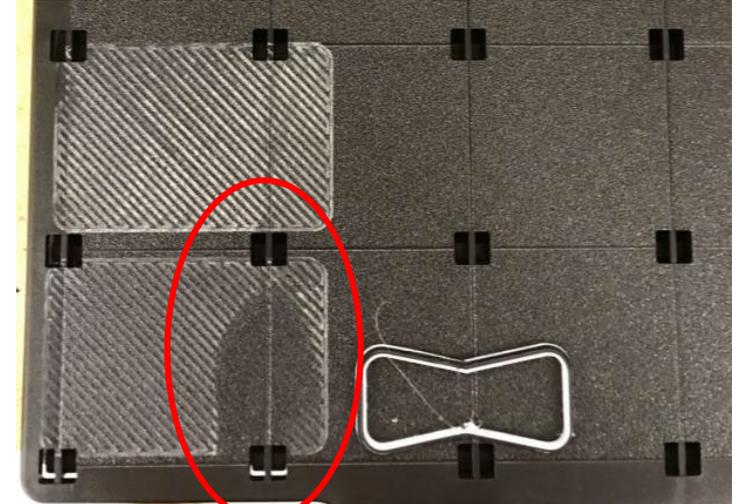

Residue from first layer is not present where oils are on substrate (indication of low adhesion). Normal handling typically leads to a build up of oil near edges and corners of substrate. This will lead to low adhesion for parts built in those areas.


HARDWARE

TPU MODIFIED HEAD DESIGN

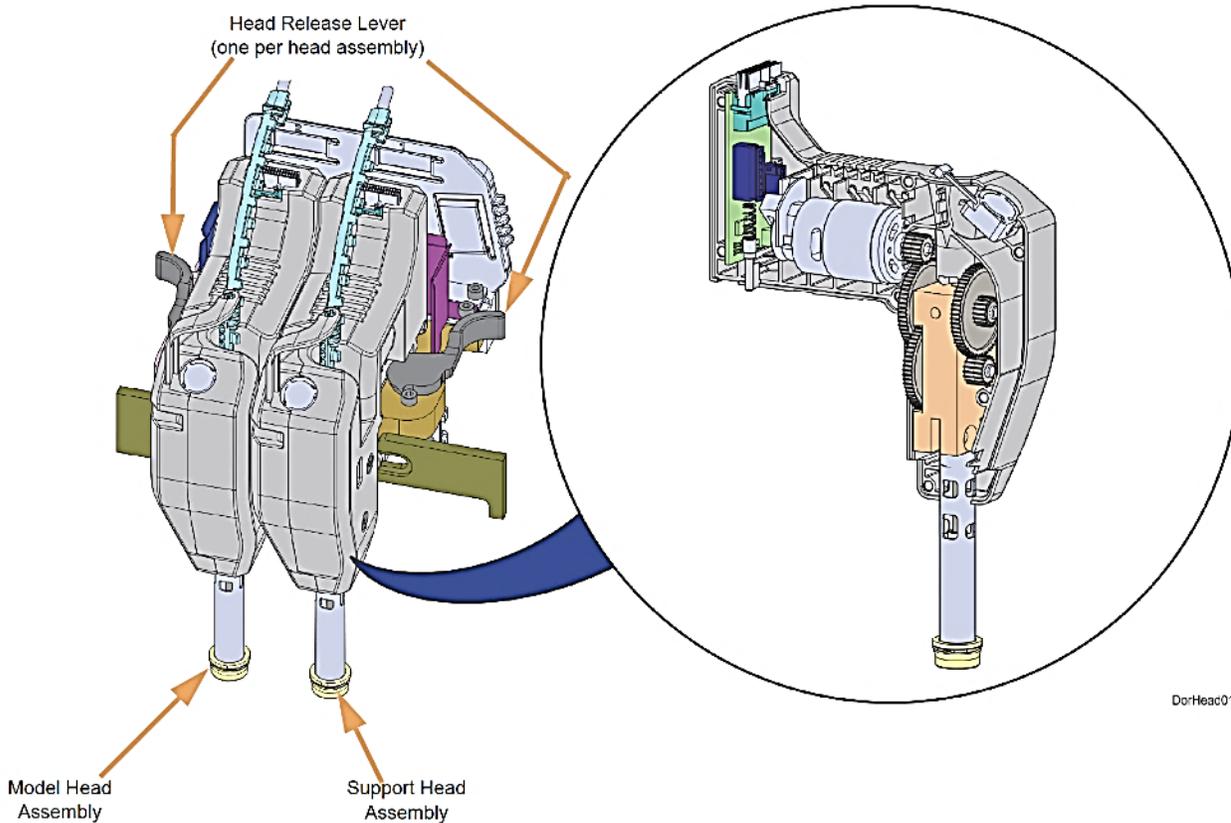

- Head Color: Blue
- Layer height: 0.010"
- T14 tip
- Consumable low mass head design
- Optimized for elastomeric material (not compatible with rigid materials)
 - Increased pinch on the filament
 - Quad Drive
- Head life:
 - 700 hrs. – Notification to order a new head.
 - 800 hrs. – Notification to replace head. Will be able to continue to print if print quality is desirable. (Standard head: 1500hrs)
 - Warranty – 90 days from install date.
- Throughput: 50% slower than ABS

MODIFIED UPPER Y-BLOCK

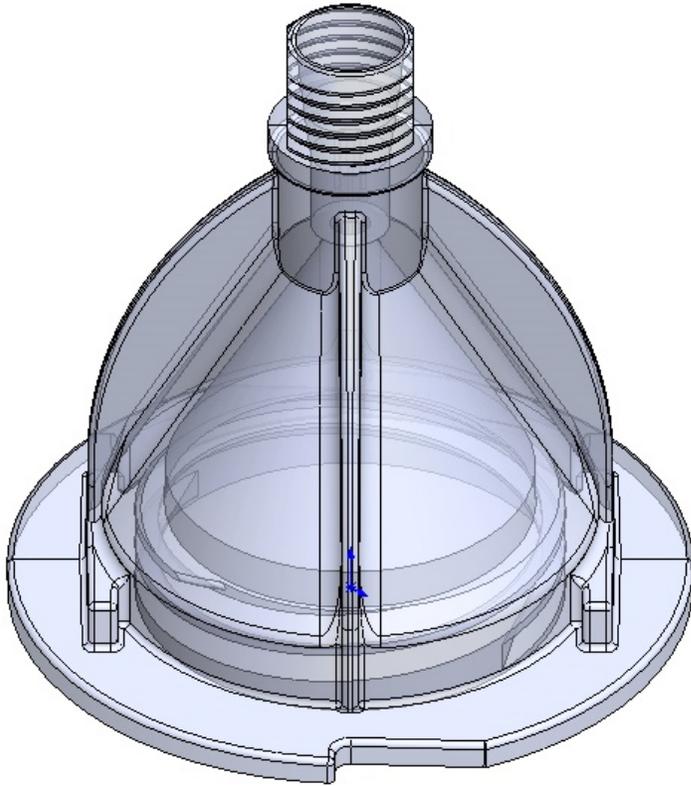

- Same part as previously used but with a media blasted interior
- Reason for replacement: fixes loading issues
 - Only the upper half of each Y-block needs to be replaced

TPU 92A TIP OFFSET CALIBRATION CHANGES

1. Perform Auto tip offset calibration
2. Perform Manual tip offset calibration on X&Y only.
 - TPU 92A adheres extremely well to QSR.
 - The automatic Z tip calibration is sufficient and manual Z calibration is not necessary.

PART QUALITY

Ripples or waves in parts:

- If you experience any waves or ripples in parts as shown on the right, please verify the following:
 - Tips and tip wipes are clean of any material debris.
 - Clean tips/tip wipes if any debris is present
 - Tip Wipes are adjusted to correct height
 - Try reorienting part for better results



SUPPORT REMOVAL TANK

Always tank the parts since manual support removal is likely to damage the part

Tank temperature: 70C

Note:

- An ultrasonic tank is most efficient (faster) for geometries with trapped cavities such as tubes
- The SCA 1200HT and the SCA 3600, which are typically used with the F123 platform, use circulation and are not ultrasonic



SCA 3600 Support Removal Tank

GRABCAD PRINT SOFTWARE


PART ORIENTATION

“Orient for stability”

- Normally, parts are oriented for function, aesthetics, speed, etc. with the expectation that parts will build successfully.
- With the F123 TPU 92A material, orienting for build success is the primary consideration. Then factors such as design intent and aesthetics can be considered.

PART ORIENTATION

- Try to minimize the Z extent
- Watch for vertical areas that can be unstable
- Insight users can further stabilize by increasing the self supporting angle (default is 55 degrees), switch to a different support style, and/or use stabilize walls

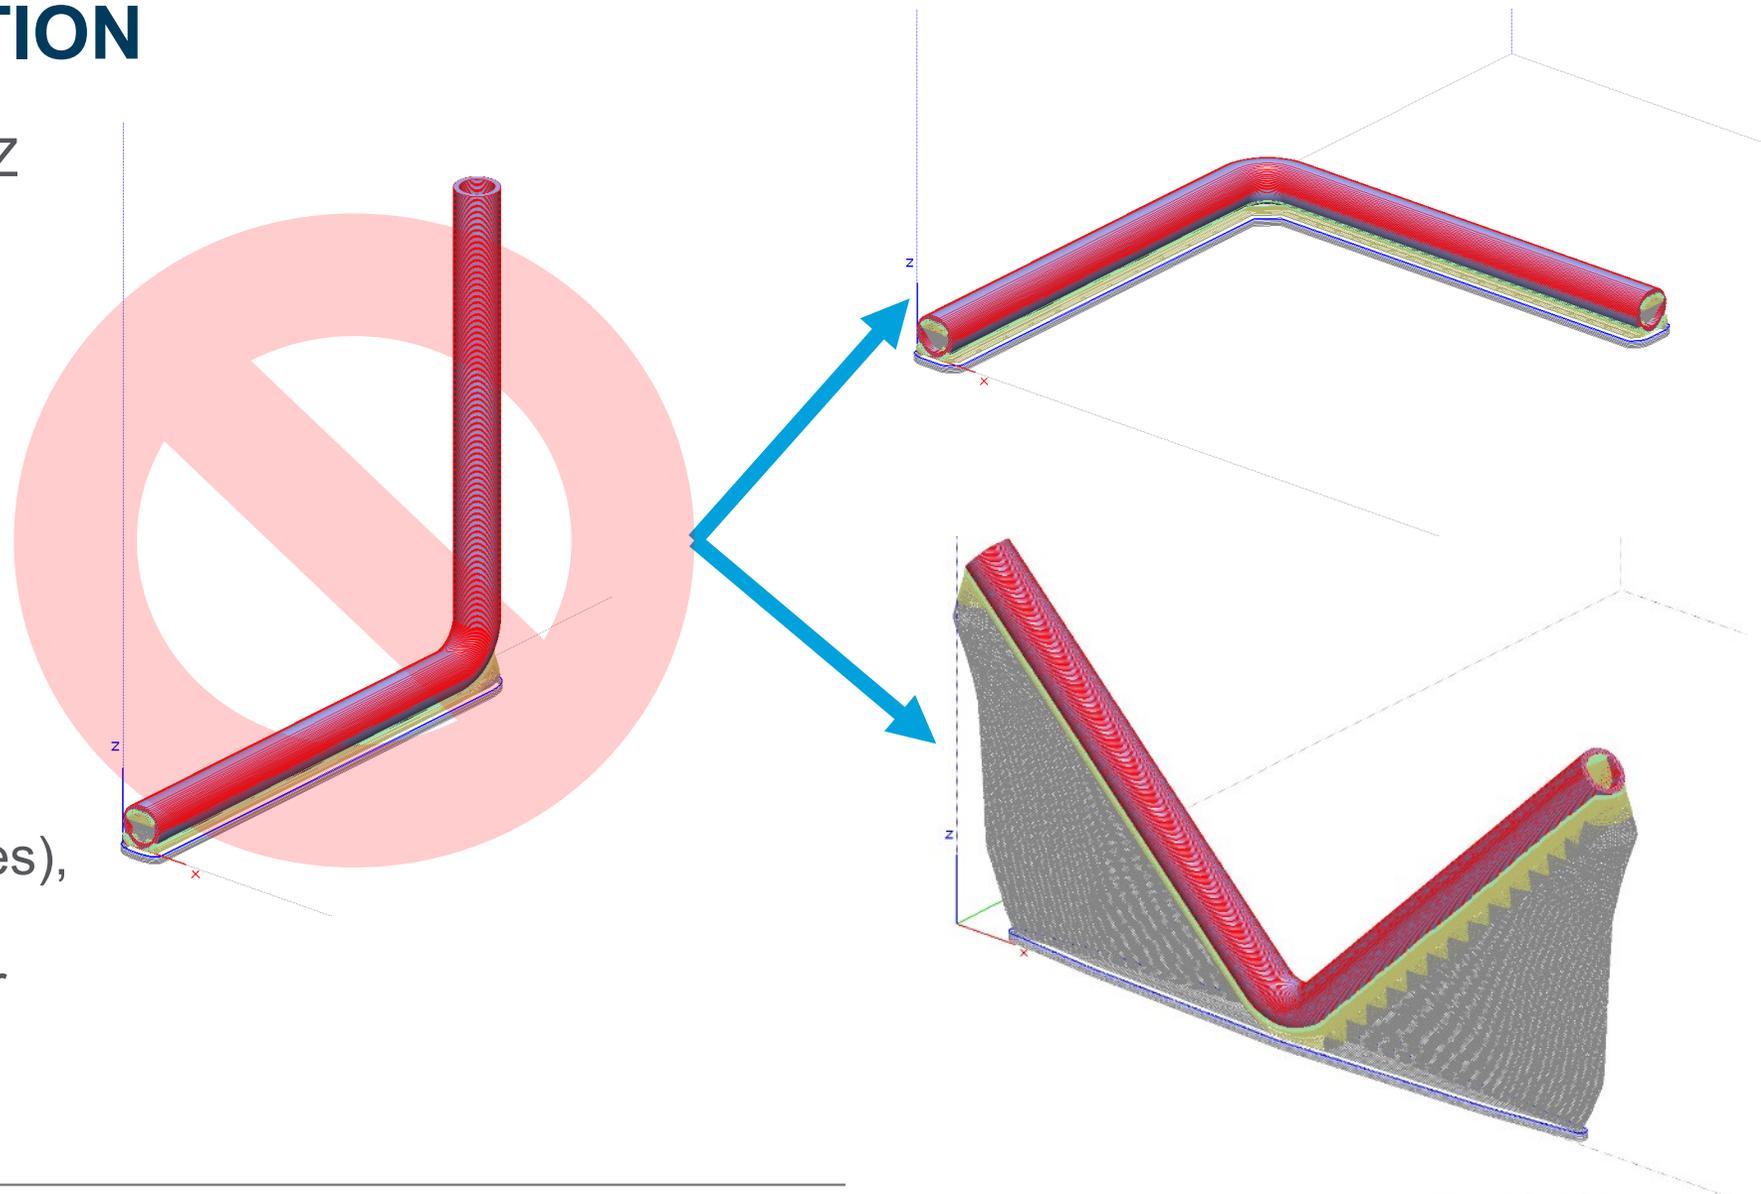

PROCESSING WITH INSIGHT

MODELER SETUP


Part interior style: High Density

Interior of High Density elastomer parts are 80% dense. We recommend against increasing this, as it may cause overfill and head jams.

Visible surface style: Enhanced

Note:

Solid, Sparse low density, and Sparse high density are not available

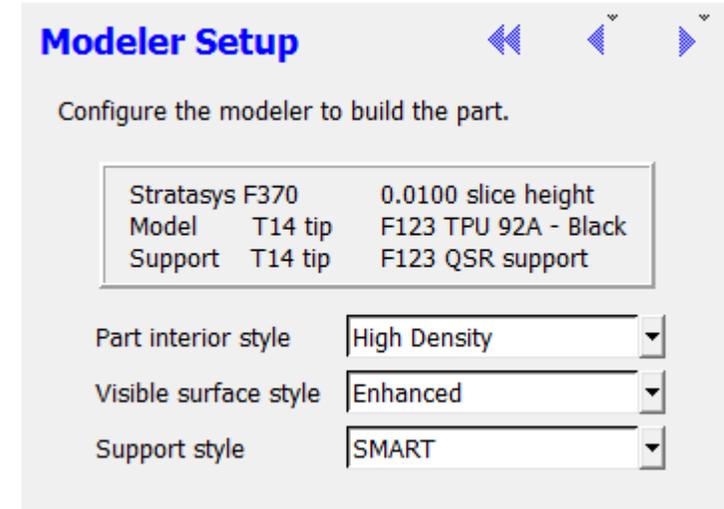

SUPPORT SETUP

Support style: Smart
Sparse and Surround are optional

Self supporting angle: 55.0000

Things to note:

- Support interface layers will leave a matte surface
- Using Surround support can leave lines on the part
- Don't use model as support

The screenshot shows the 'Support Parameters' dialog box with the following settings:

- Support Style:**
 - Support style: SMART
 - Use model material where possible
 - Use Basic fill style in model material supports
 - Circular SMART
 - Surround depth: 0.0500
 - Box partition size: 0.5000
- Base:**
 - Two layers of base top
 - Contour base
 - Base oversize: 0.0600
 - Base layers: 10
- All Supports:**
 - Self-supporting angle: 55.0000
 - Grow supports: Small only
 - Support growth angle: 1.7184
 - Supports to create: Supports and base
- Perforation:**
 - Insert perforation layers
 - Interval height: 1.0000
 - Number of Layers: 1
- Partial Supports:**
 - Starting height: 10.0000
- Other options:**
 - Two layers of support face
 - Add contour to support face

At the bottom of the dialog, there are two icons: a green checkmark and a red X.

TOOLPATH SETUP

Part fill style: Multiple contours

Visible surface style: Enhanced

Link contours: Checked

Minimize transition moves: Checked

Things to note:

- The number of contours can be increased
- Don't use variable width remnant fill
- Multiple contours helps with: sealing, seam quality (better/closed), consider two thin contours vs one larger contour.

Toolpath Parameters

Fill Style

Part fill style: Multiple contours
Visible surface style: Enhanced
Part interior style: High Density

Contours

Contour width: 0.0160
Number of contours: 2
Contour to contour air gap: 0.0000
 Link contours

Additional Settings

Part X shrink factor: 1.0080
Part Y shrink factor: 1.0080
Part Z shrink factor: 1.0049

Bypass seam placement method
 Minimize transition moves
 Use variable width remnant fill

Enhanced Surfaces

Enhanced visible rasters: 0.0135
Visible raster air gap: 0.0010
Surface max contours: 0
Enhanced internal rasters: 0.0145
Internal raster air gap: 0.0020

Raster Fill

Part raster width: 0.0145
Raster angle: 45.0000
Contour to raster air gap: 0.0000
Raster to raster air gap: 0.0020

Use parallel offset part rasters

Sparse Fill

Number of interior contours: 1
Part sparse fill air gap: 0.0350
Part sparse solid layers: 4
Sparse pattern cycle: 8
Sparse raster angle: 45.0000
 Extend bridge layer to sparse rasters
Cap layer extension: None

✓ ? ✗

PART STABILIZATION (INSIGHT)

By default, stabilize walls are built with model material.

Generally, this is fine for stabilization up to ~5”.

For better stabilization, use a custom group to build the stabilize wall out of support material.

The template shown is a modified version of PartStabilizer

Enter the new group's name and parameters.

General information

Group name: Stabilizer Wall
Description:
Display color: Magenta
Toolpath material: Support

Contour parameters

Contour style: Multiple contours
Contour width: 0.0140
Number of contours: 2

Contour controls

Apply contour style to selected feature only
 Link contours
 Allow increased contour overfill
 Bypass seam placement

Outer contour location: Inside

Air gaps between:

Adjacent rasters: 0.0073
Contours and rasters: 0.0000
Contour and contour: 0.0000

Open curves

Open curve width: 0.0145

Infill parameters

Infill style: Alternating rasters
Raster width: 0.0145
Alternate fill cell size: 0.2000
Permeable pattern cycle: 8

Align rasters

Infill angle controls

Start angle: 45.0000
Delta angle: 90.0000
Layers between deltas: 1

Sparse fill controls

Include in part sparse fill
 Add a contour around sparse

Infill style: Alternating rasters
Sparse raster width: 0.0145
Sparse raster air gap: 0.0073
Start angle: 45.0000
Delta angle: 90.0000
Alternate fill cell size: 0.2000
Permeable pattern cycle: 8

PART PACKING

Every print requires a full height purge part.

The use of a purge part enables:

- Faster head swaps
- Better control of purge material (conditions the liquefier) which ensures part quality.

Best Practices:

- Place the purge part close to the first part in the pack or next to the tallest part.

